

## Modification of human pericardium by chemical crosslinking

Elena Filová<sup>1</sup>, Lubica Staňková<sup>1</sup>, Adam Eckhardt<sup>1</sup>, Jana Svobodová<sup>1</sup>, Jana Musílková<sup>1</sup>, Jan Pala<sup>2,3</sup>, Daniel Hadraba<sup>1,4</sup>, Eduard Brynda<sup>5</sup>, Miroslav Koňářík<sup>6</sup>, Jan Pirk<sup>6</sup>, Lucie Bačáková<sup>1</sup>

<sup>1</sup>Institute of Physiology of the Czech Academy of Sciences, Department of Biomaterials and Tissue Engineering, Videnska 1083, 142 20 Prague 4, Czech Republic, elena.filova@fgu.cas.cz, lubica.stankova@fgu.cas.cz, adam.eckhardt@fgu.cas.cz, jana.svobodova@fgu.cas.cz, jana.musilkova@fgu.cas.cz, daniel.hadraba@fgu.cas.cz, lucie.bacakova@fgu.cas.cz

<sup>2</sup>Third Medical Faculty, Charles University in Prague, Institute of Pathophysiology, Ruská 87, 100 00 Prague, Czech Republic, jan.pala@lf3.cuni.cz

<sup>3</sup>National Institute of Mental Health, Topolova 749, 250 67 Klecany, Czech Republic

<sup>4</sup>Faculty of Physical Education and Sport, Charles University, Jose Martiho 31, 162 52 Prague 6, Czech Republic

<sup>5</sup>Institute of Macromolecular Chemistry, Czech Academy of Sciences, Heyrovsky Sq. 2, 162 06 Praha 6, brynda@imc.cas.cz

<sup>6</sup>Institute for Clinical and Experimental Medicine, Videnska 1958/9, 140 21 Prague 4, Czech Republic, konm@ikem.cz, jan.pirk@medicon.cz

## **Summary**

Autologous and allogenic human pericardia used as biomaterials for cardiovascular surgery are traditionally crosslinked with glutaraldehyde. In this work, we have evaluated the resistivity to collagenase digestion and the cytotoxicity of human pericardium crosslinked with various concentrations of glutaraldehyde in comparison with pericardium crosslinked by genipin, nordihydroguaiaretic acid, tannic acid, and in comparison with unmodified pericardium. Crosslinking retained the wavy-like morphology of native pericardium visualized by second harmonic generation microscopy. The collagenase digestion products were analyzed using SDS-PAGE, capillary electrophoresis, and a hydroxyproline assay. Glutaraldehyde and genipin crosslinking protected the native pericardium efficiently against digestion with collagenase III. Only low protection was provided by the other crosslinking agents. The cytotoxicity of crosslinked pericardium was evaluated using xCELLigence by monitoring the viability of porcine valve interstitial cells cultured in eluates from crosslinked pericardium. The highest cell index, reflecting both the number and the shape of the monitored cells was observed in eluates from genipin. Crosslinking pericardium grafts with genipin therefore seems to be a promising alternative procedure to the traditional crosslinking with glutaraldehyde, because it provides similarly high protection against degradation with collagenase, without cytotoxic effects.

Corresponding author: Elena Filova, Ph.D., Department of Biomaterials and Tissue Engineering, Institute of Physiology of the Czech Academy of Sciences, Videnska 1083, 142 20 Prague 4, Czech Republic, tel.: +420 29644 3742, fax: +420 244 472 269, e-mail: elena.filova@fgu.cas.cz

**Key words:** human pericardium, valve interstitial cells, chemical crosslinking, genipin, glutaraldehyde

## **Introduction**

Both autologous and allogenic human pericardium are used as biomaterials for applications in tissue regeneration (Lam and Wu 2012). Fresh autologous pericardium has desirable characteristics for cardiovascular implantation. It has been used for patches, baffles, valve substitutes and conduits in the field of surgical repairs for congenital and acquired cardiovascular defects. Autologous pericardium is non-immunogenic and free from donor-derived pathogens. In order to facilitate the handling of pericardium in surgery, its toughness and shape stability have often been improved by treatment with glutaraldehyde (GA) (Jonas 2014, Remi *et al.* 2011, Kawase *et al.* 2013). However, there is only limited availability of autologous human pericardium, due to the risk of inflammatory complications after pericardiotomy.

Allogenic human pericardium has to be processed prior to implantation in order to reduce the immunological response of the recipient's organism (Badylak and Gilbert 2008). In a traditional approach, commercially-available cryopreserved human cardiac allografts (e.g. CryoLife) (Lee *et al.* 2017) are treated with GA, as a result of which potential adverse effects of foreign cells, cell debris and possible donor-derived pathogens are disabled. However, GA-treated tissues are prone to calcification after long-term implantation (Lam and Wu 2012, Remi *et al.* 2011, Lee *et al.* 2017). Moreover, GA-fixed tissues caused an increase in circulating cytotoxic T cells, helper T cells and anti-HLA antibodies (Vinci *et al.* 2013, Welters *et al.* 2001). The inflammatory process induced by GA cytotoxicity is probably involved in the calcification mechanism (Remi *et al.* 2011).

Compared to GA-fixed bovine pericardium grafts, genipin-fixed grafts induce significantly weaker inflammatory reactions, and their regeneration is far faster (Chang *et al.* 2002). Natural compounds, such as nordihydroguaiaretic acid (NDGA), tannic acid (TA), and procyanidins, or

chemical compounds such as epoxides, carbodiimide, and others, have been used for crosslinking cardiovascular scaffolds derived from extracellular matrix (Ma et al. 2014).

In this study, the treatment of native human pericardium with genipin, NDGA and TA was compared with GA-fixation in relation to the resistivity of pericardium against digestion with collagenase III. The potential cytotoxicity of the pericardium was estimated by the growth of valve interstitial cells (VICs) in eluates from this pericardium, monitored in real-time in the sensoric xCELLigence system.

## **Methods**

### **Chemical and biochemical substances**

Glutaraldehyde (Polysciences, Inc., Cat. No.00216), genipin (Sigma, Cat. No. G4796), tannic acid (Sigma, Cat. No.96311-250G-F), and nordihydroguaiaretic acid (Sigma, Cat. No. 74540) were used for pericardium crosslinking. Collagenase III solution (Cat. No. LS004208, 149 U/ml) was purchased from Worthington Biochemical Corp. The reducing sample buffer (with sodium dodecyl sulfate SDS, 1.6%, and mercaptoethanol, 4%) used in SDS-PAGE electrophoresis, trypsin from bovine pancreas (TPCK treated) used in capillary electrophoresis, and phosphate-buffered saline, pH 7.4, (PBS) were from Sigma Aldrich. The P4417-100TAB Dulbecco-modified Eagle Minimum Essential Medium (DMEM; Gibco®; Cat. N° 52100-021) was purchased from Life Technologies Czech Republic s.r.o, and the Gentamicin was purchased from LEK, Ljubljana. The fetal bovine serum (FBS) was purchased from Sebak GmbH, Aidenbach, Germany.

### **Pericardium harvesting**

Human fibrous pericardium was harvested from the anterior part of the heart of 6 patients during open heart surgery. The pericardium samples were rectangular and their area was in the range from 18 to 32 cm<sup>2</sup>. All patients signed an informed consent form prior to enrolment in the study. The harvested pericardium was stored in DMEM cell cultivation medium supplemented with gentamicin (40 µg /mL) and 10% FBS while it was being washed with PBS. Samples for the experiments were cut off it and were weighed in wet state. The study was approved by the Ethics Committee of the Institute for Clinical and Experimental Medicine and Thomayer Hospital in Prague, approvals Nos. G 09-12-30, C.j. 2401/09, and G14-08-63, approved on August 13<sup>th</sup>, 2014.

### **Crosslinked pericardium (cP)**

Pieces of native pericardium (nP) were washed with PBS, and were crosslinked with glutaraldehyde, genipin, tannic acid or NDGA for 48 hours at room temperature. Stock 8 wt% glutaraldehyde solution was diluted with PBS. Genipin was dissolved in dimethyl sulfoxide (DMSO) into a 2.5 wt% solution and was then diluted with PBS. Tannic acid was dissolved in PBS to 2 wt% and was then diluted with PBS. NDGA was dissolved in DMSO (20 mg/ml) and was then diluted with PBS.

### **Second harmonic generation (SHG) imaging**

SHG images of native and crosslinked pericardium were acquired by the laser scanning confocal system (Leica DM IRE2 inverted microscope, Leica TCS SP2 AOBS confocal microscope and Leica TCS SP8 AOBS WLL MP confocal microscope, Germany, confocal scan head). The second harmonic signal was induced by tuning the Chameleon Ultra II laser (Coherent, Santa Clara, CA) to 860 nm linear polarized light. The incident beam reached the sample through the objective (Leica HC PL APO CS 20.0x/0.70 IMM/CORR UV CS – corr.

ring set for W), and the back-scattered SHG signal was expected at half the excitation wavelength, i.e. 430 nm, at the non-descanned PMT detector (band pass filter HQ430/20 M-2P, Chroma, USA). The nature of the SHG signal was confirmed by changing the excitation wavelength to 800 nm. The z-stack images were acquired with 10  $\mu\text{m}$ -depth thickness for voxel size 0.18:0.18:2.50  $\mu\text{m}$  [X:Y:Z].

### **Collagenase treatment**

Wet samples of native or crosslinked pericardium were washed three times in PBS and were weighed. A sample of about 100 mg was incubated at 37°C in a collagenase III solution corresponding in volume (in  $\mu\text{l}$ ) to 10 times the weight of the sample (in mg).

### **One-dimensional sodium dodecyl sulfate–polyacrylamide gel electrophoresis (SDS-PAGE)**

A part of the native or crosslinked pericardium (20  $\mu\text{g}$ ) obtained after incubation with collagenase III for 4 hours at 37°C was lyophilized and was extracted by incubation with 120  $\mu\text{L}$  of a reducing sample buffer (0.05 M tris(hydroxymethyl)aminomethan buffer pH 6.8, SDS 1.6% w/w, and mercaptoethanol 4% v/v, Sigma) for 10 minutes at 105°C with shaking. The extract solution was analysed by SDS-PAGE using homogeneous 10% polyacrylamide resolving gel according to the methods described by Laemmli (Laemmli 1970). Finally, 5  $\mu\text{l}$  of Precision Plus Protein™ Standards (molecular weight range 10-250 kDa, Bio-Rad) was added at the top end of the gel. The gels were released into the Mini-Protean® Tetra cell system (Bio-Rad) at 200 V until the bromophenol blue reached the end of the gel (ca 45 min). The gels were then stained with Bio-Safe™ Coomassie Blue G250 Stain (Bio-Rad). After staining, the gels were washed with water, were scanned with a GS-800 Calibrated Densitometer, and were processed with image analysis software (Quantity One®, Bio-Rad).

### **Capillary electrophoresis**

Samples of pericardium were treated with collagenase III for 4 hours, and were dried, were digested for 5 hours using trypsin (0.2 mg/ml, 0.1 M  $\text{NH}_4\text{HCO}_3$ , pH 7.8), were boiled for 15 minutes at 105°C, were dried and were again immersed into trypsin of the same concentration for 5 hours. The trypsin-to-dry-sample weight ratio was kept at 1:100. The twice digested samples were dried, dissolved in the electrophoretic buffer, were sonicated for 15 minutes and were filtered using a 0.20  $\mu\text{m}$  filter (Millex-LG, Japan). The final concentration of each sample was 10 mg/mL (calculated to the dry weight of the tissue).

Electrophoretic separations were performed using Beckmann P/ACE System 5500 apparatus with UV detection set to 214 nm. For all separations, we used a fused silica capillary 37 cm in total length (30 cm to the detector) and 75  $\mu\text{m}$  in inner diameter (Composite Metal Service LTD, The Chase, Hallow, Worcs., UK). All separations were run in 0.1 M phosphate buffer, pH 2.50. For each electrophoretic experiment, 20  $\mu\text{l}$  of sample solution was pipetted; the duration of injection was set to 3s. The separation voltage was set to 10 kV at 20°C, and the separation time was 80 minutes. Before each electrophoresis, the capillary was prewashed with water, 1 M HCl, water and running buffer, with 2 minutes for each step.

### **Hydroxyproline assay**

The solutions that had arisen after 1, 2, 3, and 4 hours treatment of native pericardium or after 1 and 3 hours treatment of crosslinked pericardium with collagenase III at 37°C were tested using the Hydroxyproline assay kit (BioVision, Cat. No. K555-100). Briefly, 100  $\mu\text{l}$  of sample solution with 100  $\mu\text{l}$  of HCl (36%) was incubated for 3 hours at 120°C. Ten  $\mu\text{l}$  of the solutions in triplicate were pipetted into a 96-well plate, were dried out, and 100  $\mu\text{l}$  of chloramin T reagent was added and then incubated for 5 min. Finally, 100  $\mu\text{l}$  4-(*N,N*-dimethylamino)-benzaldehyde (DMAB) reagent was added, was incubated at 60°C for 90 min, and was measured at 560 nm

on a VERSAmax tunable microplate reader (Molecular Devices). A calibration curve was prepared by adding hydroxyproline standard into the wells at a concentration of 0, 0.2, 0.4, 0.6, 0.8, and 1  $\mu\text{g}$  per well.

### **xCELLigence (Cell Index)**

Native and crosslinked pericardium samples were washed with PBS containing 0.2 M glycine and 2.5% Antibiotic Antimycotic solution (all chemicals from Sigma-Aldrich) for 14 days, replacing the buffer each day. Glycine could deactivate residues of the crosslinking agents capable of producing a covalent reaction with amine groups. Then eluates were prepared by incubating pericardium samples with DMEM supplemented with gentamicin (40  $\mu\text{g}/\text{mL}$ ) for 3 days; 1  $\text{cm}^2$  of the sample was used per 1mL of the medium. The eluates were supplemented with 10% FBS and were used for the cultivation of porcine VICs seeded at a density of 3000 cells/200  $\mu\text{l}$  on the bottoms of the wells in a microtiter plate (E-Plate 96, Cat. No. 077601, Acea Biosciences, Inc., CA, U.S.A.).

The cell index, reflecting the number and the spreading area of the seeded cells, was determined using the xCELLigence System (Roche Applied Science) on day 5 after seeding. The cell index of the VICs cultivated in DMEM supplemented with gentamicin and 10% FBS was used as a control. Passages 3-7 of the VICs isolated and characterized according to Liskova *et al.* (Liskova *et al.* 2017) were used for the experiments.

## **Results**

### **SHG imaging**

Figure 1 shows SHG images of multilayered, multidirectionally oriented and overlapping collagen fiber bundles forming a densely woven network in fibrous pericardium. The typical

collagen structure of native pericardium (Straka et al. 2018), was preserved after crosslinking with any of the crosslinking agents.

### **SDS-PAGE electrophoresis**

The SDS-PAGE electropherograms of extracts from nP in Figure 2 show typical bands of collagen fragments obtained by collagenase digestion at 37°C (Shoulders and Raines 2009). If pericardium was crosslinked with increasing concentrations of GA (Fig. 2 a) or genipin (Fig. 2 b), the absence of a collagen part alpha 2 band at about 104 kDa was observed in extracts from pericardium crosslinked with GA *0.016 M* or genipin *0.0044 M*. The band of collagen part alpha 1 at about 142 kDa disappeared at concentrations of GA *0.016 M* or genipin *0.011 M*. Collagen chains alpha 1 and alpha 2 were detectable in the extracts from pericardium treated with NDGA (Fig. 2 c) at all used concentrations (*0.0017-0.013 M*). Almost no differences could be distinguished between the SDS images of the extracts obtained from nP and from pericardium crosslinked with TA (Fig. 2 d).

### **Capillary electrophoresis**

Figure 3 shows oligo- and poly-peptide peaks in electropherograms obtained by capillary electrophoresis of solutions prepared by trypsinization of collagenase-treated nP and crosslinked pericardium. The electropherogram profile of the solution from nP was not changed when the pericardium was treated with GA at a concentration of *0.0004 M* (Fig. 3a, curves *a* and *b*). Most peaks disappeared at a GA concentration of *0.0064 M* (Fig. 3 a, curve *c*). A further increase in GA concentration had only a minor influence on the electropherograms. The peaks of peptides that appeared before 40 minutes were absent in the electropherograms obtained from pericardium crosslinked with genipin at a concentration of *0.0022 M* (Fig. 3 b, curve *b*), and all peaks disappeared when higher genipin concentrations were used. The increase in NGDA

concentration decreased peak areas without changing profiles of the electropherograms (Fig. 3 c). Similarly, the profiles of the electropherograms did not change if pericardium was crosslinked with TA, with the exception of an unexplained increase in the peak appearing at 14 minutes in the electropherograms if the TA concentration was increased above  $0.00059\text{ M}$  (Fig. 3 d, curve *c*).

### **Hydroxyproline content**

Figure 4 shows the amounts of hydroxyproline (HP) released from nP during incubation with collagenase. The mass of the released HP increased linearly with increasing time of incubation, and reached  $0.35\text{ }\mu\text{g/mL}$  for 1 hour of incubation and  $0.62\text{ }\mu\text{g/mL}$  for 3 hours of incubation. The mean values of HP (Fig. 5 a) released during 1 h of incubation with collagenase from pericardium crosslinked with GA at any of the concentrations used here ( $0.4\text{-}0.00004\text{ M}$ ), and during 3 h from pericardium crosslinked with GA concentrations from  $0.4\text{ to }0.004\text{ M}$ , were scattered round  $0.07\text{ }\mu\text{g/mL}$ . The amount of HP released during 3 h increased significantly to  $0.3\text{ }\mu\text{g/mL}$  if the GA concentration was decreased to  $0.0004\text{ M}$ , and to  $0.54\text{ }\mu\text{g/mL}$  if the GA concentration was reduced to  $0.00004\text{ M}$ . The mean values of HP (Fig. 5 b) released during 1 h of incubation from pericardium crosslinked with genipin at any of the used concentrations ( $0.022\text{-}0.0022\text{ M}$ ), and during 3 h from pericardium crosslinked with genipin at concentrations from  $0.022\text{ to }0.0044\text{ M}$ , were scattered round  $0.1\text{ }\mu\text{g/mL}$ . The amount of HP released during 3 h increased to  $0.13\text{ }\mu\text{g/mL}$  if the genipin concentration was  $0.0022\text{ M}$ . The mean values of HP (Fig. 5 c) released from pericardium crosslinked with NGDA during 1 h of incubation increased gradually from about  $0.09\text{ }\mu\text{g/mL}$  to  $0.41\text{ }\mu\text{g/mL}$  with decreasing NGDA concentration from  $0.013\text{ to }0.0033\text{ M}$ . The mean values of HP released during 3 h increased from about  $0.11\text{ }\mu\text{g/mL}$  at NGDA concentrations of  $0.013\text{ M}$  and  $0.0066\text{ M}$  to  $0.57\text{ }\mu\text{g/mL}$  and  $0.73\text{ }\mu\text{g/mL}$  at NGDA concentrations of  $0.0033\text{ M}$  and  $0.0017\text{ M}$ , respectively. The mean values of HP (Fig. 5 d)

released during 1 h from pericardium crosslinked with tannic acid (TAcP) were scattered close to 0.03  $\mu\text{g}/\text{mL}$ . The HP released during 3 h increased linearly from 0.029  $\mu\text{g}/\text{mL}$  at a TA concentration of 0.012 M to 0.35  $\mu\text{g}/\text{mL}$  at TA 0.00029 M.

### **Cell index of porcine valve interstitial cells (VICs) cultivated in eluates from pericardium samples**

The cell index of VICs (CI) was measured on day 5 after cell seeding in a medium containing eluates from nP and crosslinked human pericardium. The CI of VICs cultivated in eluates from nP did not differ significantly from the CI in the control pure medium (Fig. 6 a) or was significantly lower (Fig. 6 b, c). By contrast, nP modification with genipin or NGDA increased the CI (Fig. 6 b). Observations indicated that some cytotoxic compounds were released from nP into the eluates, and that crosslinking fixed the compounds inside the pericardium. A statistically significant increase in CI was observed if nP was fixed with genipin at a concentration of 0.022 M; at lower concentrations, the CI was lower. Conversely, CI increased with a decreasing NGDA concentration. Figure 6 A indicates that the mean values of CI increased if nP was crosslinked with decreasing GA concentrations from 0.4 to 0.00256 M, and that the mean values decreased if the GA concentrations were further decreased. A similar trend is indicated by figure 6 c, in which CI increases with decreasing TA concentration from 0.012 to 0.0015 M (Fig.6 c). While the CI of pericardium fixed with the highest-used concentration of GA was similar to that of nP, the CI was reduced considerably by crosslinking with the highest-used concentration of TA. Some cytotoxicity of GA or TA seemed to reduce the favourable effect of the fixation, which was observed with genipin and NGDA.

## Discussion

As the scaffold of human pericardium tissue is formed mainly from fibres of collagen types I and III, the biological degradation of collagen has a substantial effect on the durability and the function of pericardium-based cardiovascular grafts. The resistance of pericardium to digestion with collagenase at 37°C has been studied in this work as an indicator of the susceptibility of pericardium to *in vivo* degradation.

SDS-PAGE, capillary electrophoresis, and hydroxyproline assay indicated that while an efficient protection against the collagen degradation was reached by the fixation of pericardium with GA or genipin, only minimum protection was obtained by the fixation with NDGA or TA. The results might be understood in the light of various mechanisms of the pericardium fixation on the process of collagen digestion with collagenase. Collagen fibres are formed by tropocollagen molecules made up of three  $\alpha$ -helix polypeptide chains (Shoulders and Raines 2009, Bunyaratavej and Wang 2001). Collagenase initiates collagen degradation by locally unwinding the triple-helical tropocollagen structure before cleaving  $\alpha$  chains at specific sites (Chung *et al.* 2004).

GA monomers and oligomers crosslink pericardium by the formation of covalent bonds between their aldehyde groups and primary amine groups of lysine or hydroxylysine amino acid residues that are located at various sites of the pericardium structure (mainly in collagen and also in minor proteins) (Mingeault *et al.* 2004). Like GA, genipin crosslinks proteins by reacting with primary amino groups. By a two-stage reaction, genipin can form dimeric genipin crosslinks within a tropocollagen molecule, or oligomeric genipin bridges between tropocollagens, or collagen microfibrils in the pericardium (Sung *et al.* 2003). Multipoint covalent crosslinking probably hinders collagen digestion due to the inability of the collagenase to penetrate inside the collagen fibers and fibrils, and by the inability to unwind triple-helical tropocollagen regions, or because of changes in the collagen structure at the cleavable sites.

Unlike GA and genipin, NDGA and TA do not crosslink collagen via forming covalent bonds with amino groups. NDGA fixes pericardium by the formation of a bisquinone polymer network, in which the collagen fibrils are embedded (Koob and Hernandez 2002, 2003). Collagen can be digested when collagenase penetrates to the fibrils. The crosslinking of collagen fibrils with TA at physiological pH is mediated mainly by non-covalent hydrogen bonding with multiple TA phenolic hydroxyl groups, and by hydrophobic interactions with TA aromatic rings (Ma et al. 2014). The time lag and the subsequent facilitation of collagenase digestion shown in Figure 5 may be due to loosening of the densely-packed collagen fibrils after non-covalently bound TA has been partially released from the pericardium.

The low viability of VICs seeded in eluates from GA crosslinked pericardium (Fig. 5a) corresponded with general GA toxicity and the cytotoxicity of GA grafts (Gough JE et al. 2002). On the other hand, some cytotoxicity of genipin, which was found to be approx. 10,000 times lower than that of glutaraldehyde (Sung *et al.* 1999), decreased the positive effect of eluates from genipin crosslinked pericardium on the VICs viability. A weak cytotoxicity of NDGA (Koob TJ et al. 2001) was probably responsible for decreasing VICs viability with increasing NDGA concentration used for the fixation of pericardium (Fig. 5c).

Collagenase digestion of native human pericardium and of pericardium treated with glutaraldehyde, genipin, nordihydroguaiaretic acid and tannic acid has been studied *in vitro* in order to suggest ways in which the susceptibility of pericardium to *in vivo* degradation could be decreased. The results have indicated that covalent crosslinking of pericardium with GA or with genipin provided similarly efficient protection against collagenase digestion, while almost no protection was achieved by non-covalent fixation with NDGA or with TA. In addition, the viability of porcine valve interstitial cells was significantly higher when they were cultivated in eluates from genipin-crosslinked pericardium than when they were cultivated in eluates from pericardium fixed by traditional crosslinking with GA.

## References


- BADYLAK SF, GILBERT TW: Immune response to biologic scaffold materials. *Semin Immunol* **20**: 109-116, 2008.
- BUNYARATAVEJ P, WANG HL: Collagen membranes: a review. *J Periodontol.* **72**: 215-229, 2001.
- CHANG Y, TSAI CC, LIANG HC, SUNG HW: In vivo evaluation of cellular and acellular bovine pericardia fixed with a naturally occurring crosslinking agent (genipin). *Biomaterials* **23**: 2447–2457, 2002.
- CHUNG L, DINAKARPANDIAN D, YOSHIDA N, LAUER-FIELDS JL, FIELDS GB, VISSE R, NAGASE H: Collagenase unwinds triple-helical collagen prior to peptide bond hydrolysis. *EMBO J.* **23**: 3020-3030, 2004.
- JONAS RA: Comprehensive surgical management of congenital heart disease, 2<sup>nd</sup> ed. CRC Press, Taylor & Francis Group, Boca Raton, London, New York, 2014, pp. 247-248.
- KAWASE I, OZAKI S, YAMASHITA H, UCHIDA S, NOZAWA Y, MATSUYAMA T, TAKATO M, HAGIWARA S: Aortic valve reconstruction with autologous pericardium for dialysis patients. *Interact Cardiovasc Thorac Surg* **16**: 738-742, 2013.
- KOOB TJ, HERNANDEZ DJ: Material properties of polymerized NDGA-collagen composite fibers: development of biologically based tendon constructs. *Biomaterials* **23**: 203-212, 2002.
- KOOB JT, HERNANDEZ DJ: Mechanical and thermal properties of novel polymerized NDGA–gelatin hydrogels. *Biomaterials* **24**: 1285-1292, 2003.
- LAEMMLI UK: Cleavage of structural proteins during the assembly of the head of bacteriophage T4. *Nature* **227**: 680-685, 1970.
- LAM MT, WU JC: Biomaterial applications in cardiovascular tissue repair and regeneration. *Expert Rev Cardiovasc Ther* **10**:1039-1049, 2012.

- LEE C, LIM HG, LEE CH, KIM YJ: Effects of glutaraldehyde concentration and fixation time on material characteristics and calcification of bovine pericardium: implications for the optimal method of fixation of autologous pericardium used for cardiovascular surgery. *Interact Cardiovasc Thorac Surg* **24**: 402-406, 2017.
- LISKOVA J, HADRABA D, FILOVA E, KONARIK M, PIRK J, JELEN K, BACAKOVA L: Valve interstitial cell culture: Production of mature type I collagen and precise detection. *Microsc Res Tech* **80**: 936-942, 2017.
- MA B, WANG X, WU C, CHANG J: Crosslinking strategies for preparation of extracellular matrix-derived cardiovascular scaffolds. *Regen Biomater* **1**: 81-89, 2014.
- MIGNEAULT I, DARTIGUENAVE C, BERTRAND MJ, WALDRON KC: Glutaraldehyde: behavior in aqueous solution, reaction with proteins, and application to enzyme crosslinking. *Biotechniques* **37**: 790-796, 798-802, 2004.
- REMI E, KHELIL N, DI CENTA I, ROQUES C, BA M, MEDJAHED-HAMIDI F, CHAUBET F, LETOURNEUR D, LANSAC E, MEDDAHI-PELLE A: Pericardial processing: challenges, outcomes and future prospects. In: *Biomaterials science and engineering*. R. PIGNATELLO (ed), IntechOpen, London, UK, 2011. pp. 437-456.
- SHOULDERS MD, RAINES RT: Collagen structure and stability. *Annu Rev Biochem* **78**: 929-958, 2009.
- STRAKA F, SCHORNIK D, MASIN J, FILOVA E, MIREJOVSKY T, BURDIKOVA Z, SVINDRYCH Z, CHLUP H, HORNY L, DANIEL M, MACHAC J, SKIBOVÁ J, PIRK J, BACAKOVA L. A human pericardium biopolymeric scaffold for autologous heart valve tissue engineering: cellular and extracellular matrix structure and biomechanical properties in comparison with a normal aortic heart valve. *J Biomater Sci Polym Ed* **29**: 599-634, 2018.


- SUNG HW, HUANG RN, HUANG LL, TSAI CC: In vitro evaluation of cytotoxicity of a naturally occurring cross-linking reagent for biological tissue fixation. *J Biomater Sci Polymer Ed* **10**: 63-78, 1999.
- SUNG HW, CHANG WH, MA CY, LEE MH: Crosslinking of biological tissues using genipin and/or carbodiimide. *J Biomed Mater Res A* **64**: 427-438, 2003.
- VINCI C, TESSITORE G, CASTIGLIONI L, PRANDI F, SONCINI M, SANTORO R, CONSOLO F, COLAZZO F, MICHELI B, SIRONI L, POLVANI G, PESCE M: Mechanical compliance and immunological compatibility of fixative-free decellularized/cryopreserved human pericardium. *Plos One* **8**: e64769, 2013.
- WELTERS MJ, OEI FB, VAESSEN LM, STEGMANN AP, BOGERS AJ, WEIMAR W: Increased numbers of circulating donor-specific T helper lymphocytes after human heart valve transplantation. *Clin Exp Immunol* **124**: 353-358, 2001.
- GOUGH JE, SCOTCHFORD CA, DOWNES S: Cytotoxicity of glutaraldehyde crosslinked collagen/poly(vinyl alcohol) films is by the mechanism of apoptosis. *J Biomed Mater Res* **61**: 121-30, 2002.
- KOOB TJ, WILLIS TA, HERNANDEZ DJ: Biocompatibility of NDGA-polymerized collagen fibers. I. Evaluation of cytotoxicity with tendon fibroblasts in vitro. *J Biomed Mater Res* **56**: 31-39, 2001.

### **Acknowledgements**

This study was supported by Czech Health Research Council projects No. 15-29153A and NV18-02-00422, by MEYS (LM2015062 Czech-BioImaging), and by BIOCEV – Biotechnology and Biomedicine Centre of the Academy of Sciences and Charles University project CZ.1.05/1.1.00/02.0109, funded by the European Regional Development Fund.

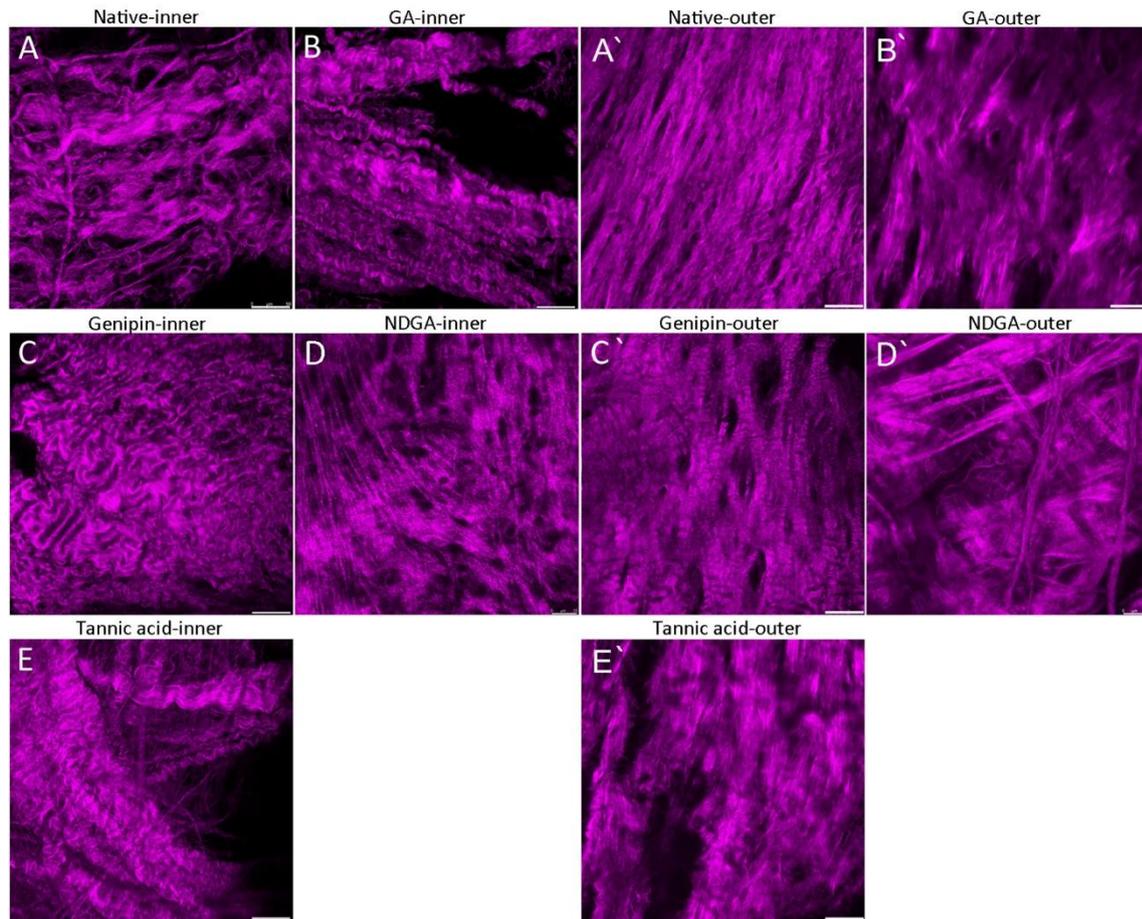

**Fig. 1.** Second harmonic generation images of fibrillar collagen in the inner side (A-E) (close to the heart) and the outer side (reverse to the heart) (A'-E') of human pericardium. Native pericardium (A, A') was treated with glutaraldehyde 0.40 M (B, B'), genipin 0.022 M (C, C'), NDGA 0.013 M (D, D'), and tannic acid 0.012 M (E, E'), Leica SP2 confocal microscope, objective  $\times 20$ , zoom  $\times 2$ , scale bar = 50  $\mu\text{m}$  (A-C, E, A'-C', E'), Leica TCS SP8 AOBS WLL MP confocal microscope, scale bar = 25  $\mu\text{m}$  (D, D') in the bottom right corner of the images.

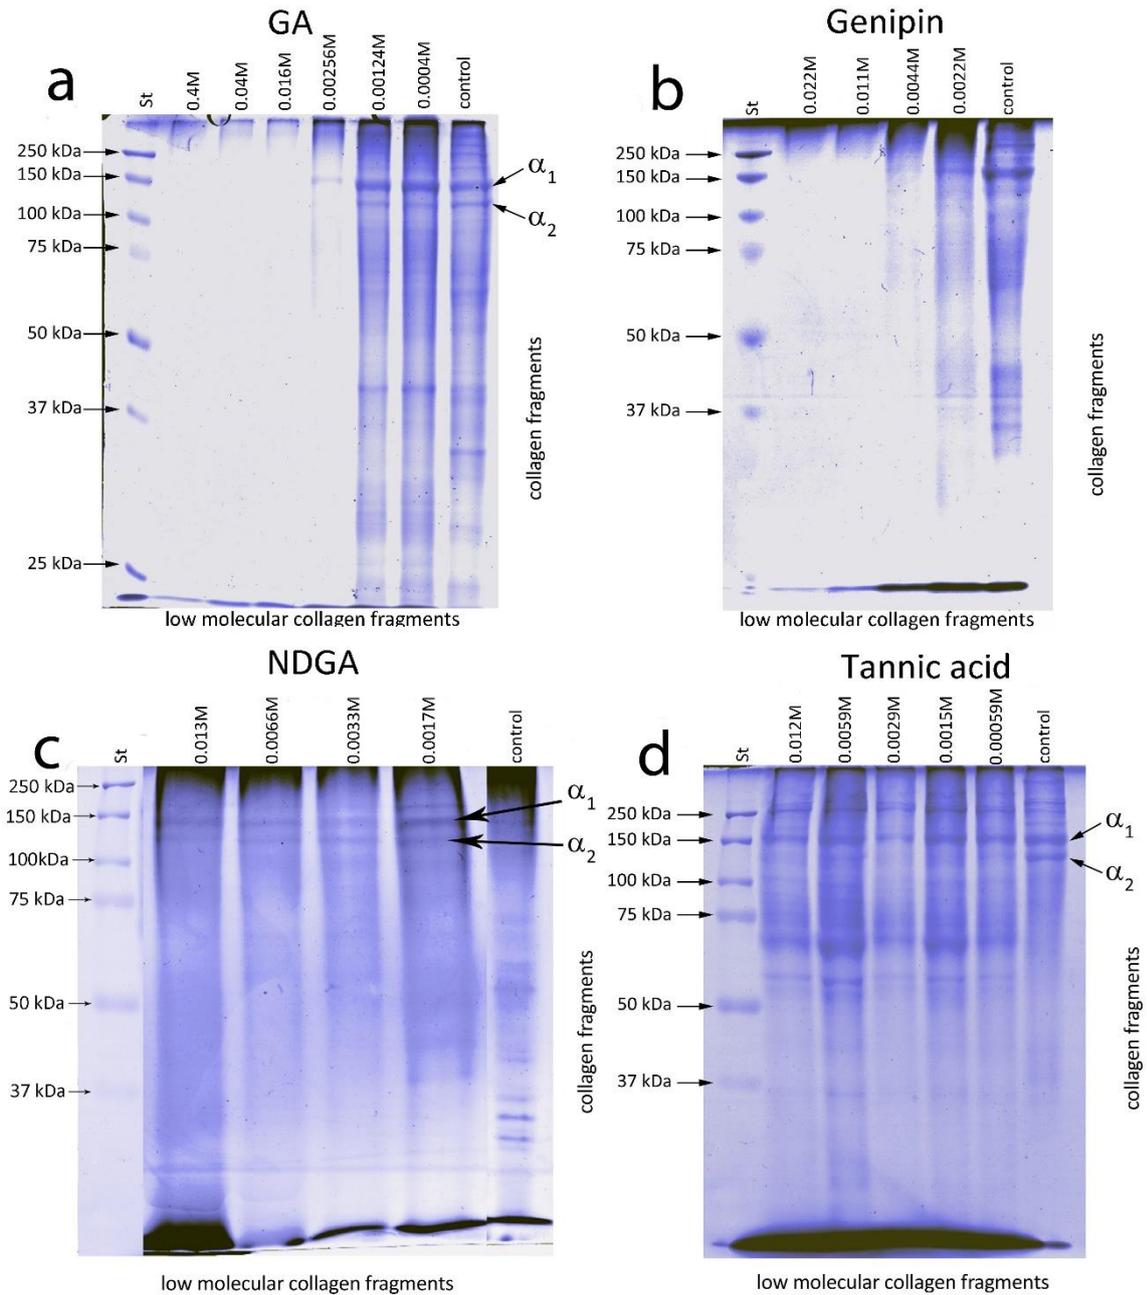


**Fig. 2.** 1D SDS-PAGE of collagen fragments extracted from human pericardium after incubation with collagenase III for 4 hours at 37°C. Pericardium was treated with (a) glutaraldehyde (GA) at concentrations of - 0.40, 0.040, 0.016, 0.00256, 0.00124, 0.0004, and 0.0 M (control), (b) genipin at concentrations of 0.022, 0.011, 0.0044, 0.0022 M and 0.0 M (control), (c) NDGA at the concentrations of 0.013, 0.0066, 0.0033, 0.0017 M and 0.0 M

(control), (d) tannic acid at concentrations of 0.012, 0.0059, 0.0029, 0.0015, 0.00059, and 0.0


M. St - molecular weight standards.

**Table 1.** The concentrations of glutaraldehyde, genipin, NDGA and tannic acid.


<i>Glutaraldehyde</i>		<i>Genipin</i>	
wt%	M	wt%	M
0.004	0.0004	0.05	0.0022
0.0124	0.00124	0.1	0.0044
0.0256	0.00256	0.25	0.011
0.16	0.016	0.5	0.022
0.4	0.04	<i>Tannic acid</i>	
4.0	0.4	wt%	M
<i>NDGA</i>		0.05	0.00029
mg/mL	M	0.1	0.00059
0.5	0.0017	0.25	0.0015
1	0.0033	0.5	0.0029
2	0.0066	1	0.0059
4	0.013	2	0.012

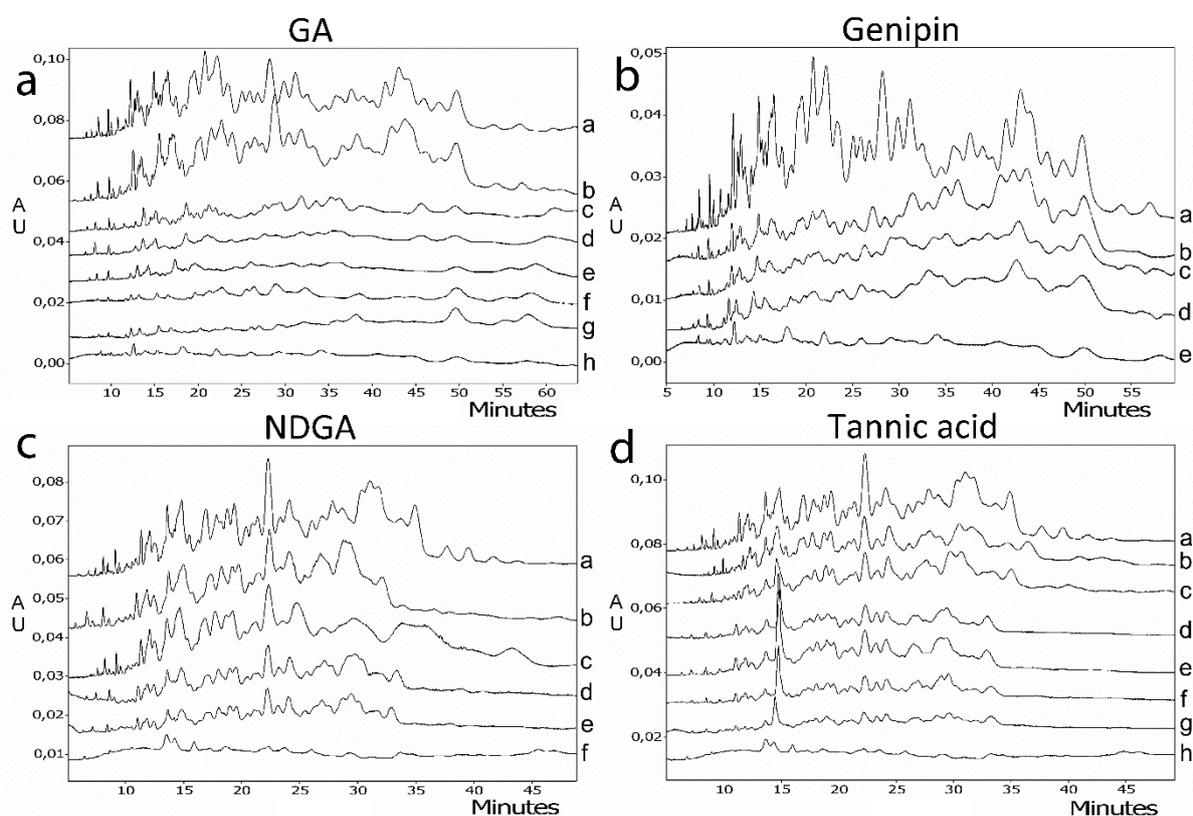


**Fig. 3.** Capillary electrophoresis of tryptic digests of pericardium (concentration of sample: 10 mg/ml) crosslinked with (a) glutaraldehyde (GA) at concentrations of  $a=0$  M (control);  $b=0.0004$  M;  $c=0.00124$  M;  $d=0.0064$  M;  $e=0.016$  M;  $f=0.04$  M;  $g=0.4$  M;  $h$ =only trypsin (without sample), (b) genipin at concentrations of  $a=0\%$  (control);  $b=0.0022$  M;  $c=0.011$  M;  $d=0.022$  M;  $e$ =only trypsin (without sample), (c) NDGA at concentrations of  $a=0$  (control);  $b=0.0017$  M;  $c=0.0033$  M;  $d=0.0066$  M;  $e=0.013$  M;  $f$ =only trypsin (without sample), and (d) tannic acid at concentrations of  $a=0\%$  (control);  $b=0.00029$  M;  $c=0.00059$  M;  $d=0.0015$  M;  $e=0.0029$  M;  $f=0.0059$  M;  $g=0.012$  M;  $h$ =only trypsin (without sample). Pericardium was incubated with collagenase for 4 hours at 37 °C before trypsinization

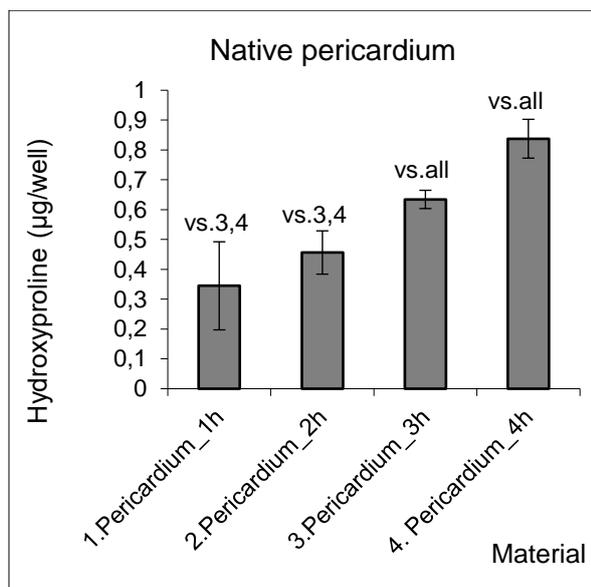

**Fig. 4.** The amount of hydroxyproline released from native pericardium (from three to six samples of each group) during incubation with collagenase III for 1, 2, 3, and 4 hours. Data expressed as mean  $\pm$  S.D., statistical significance ( $p \leq 0.05$ ) is labelled above the column in comparison with the sample of the same number. Statistical analysis ANOVA (Student-Newman-Keuls method).

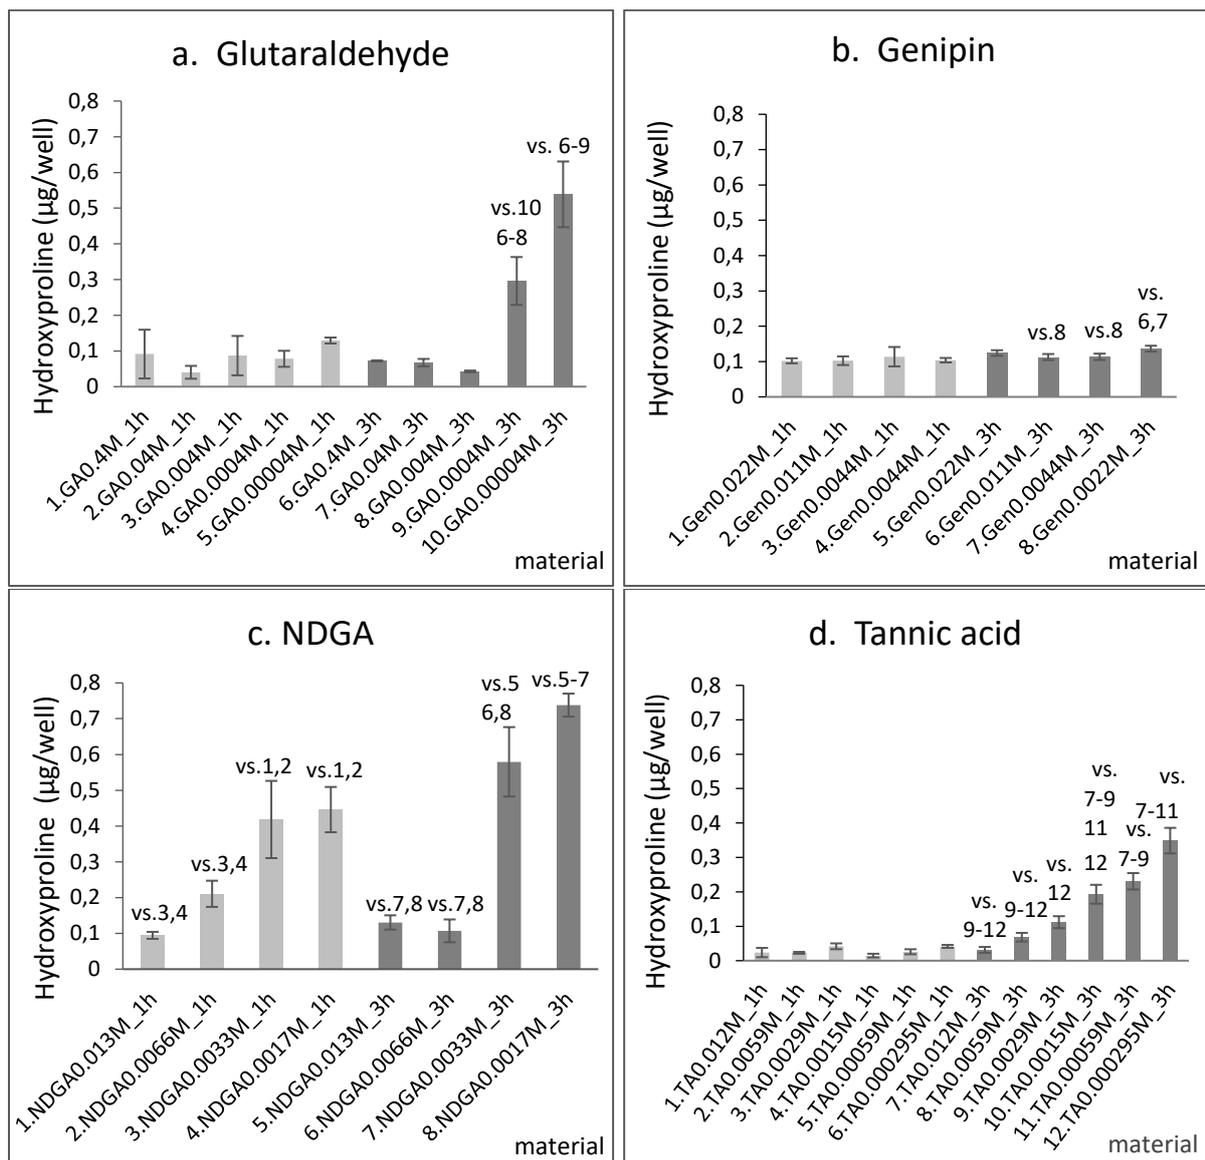

**Fig. 5.** The amount of hydroxyproline released from crosslinked pericardium during incubation with collagenase III for 1 and 3 hours. Pericardium was crosslinked with (a) glutaraldehyde at concentrations of 0.4, 0.04, 0.004, 0.0004, and 0.00004 M, (b) genipin 0.022, 0.011, 0.0044, 0.0022 M, (c) NDGA 0.013, 0.0066, 0.0033, and 0.0017 M, and (d) tannic acid 0.012, 0.0059, 0.0029, 0.0015, 0.00059, and 0.00029 M. Data are expressed as mean  $\pm$  S.D., statistical significance was considered for  $p \leq 0.05$  and was labelled above the column in comparison with the sample of the same number, from 3-6 samples of each group, statistical analysis ANOVA, Student-Newman-Keuls method.

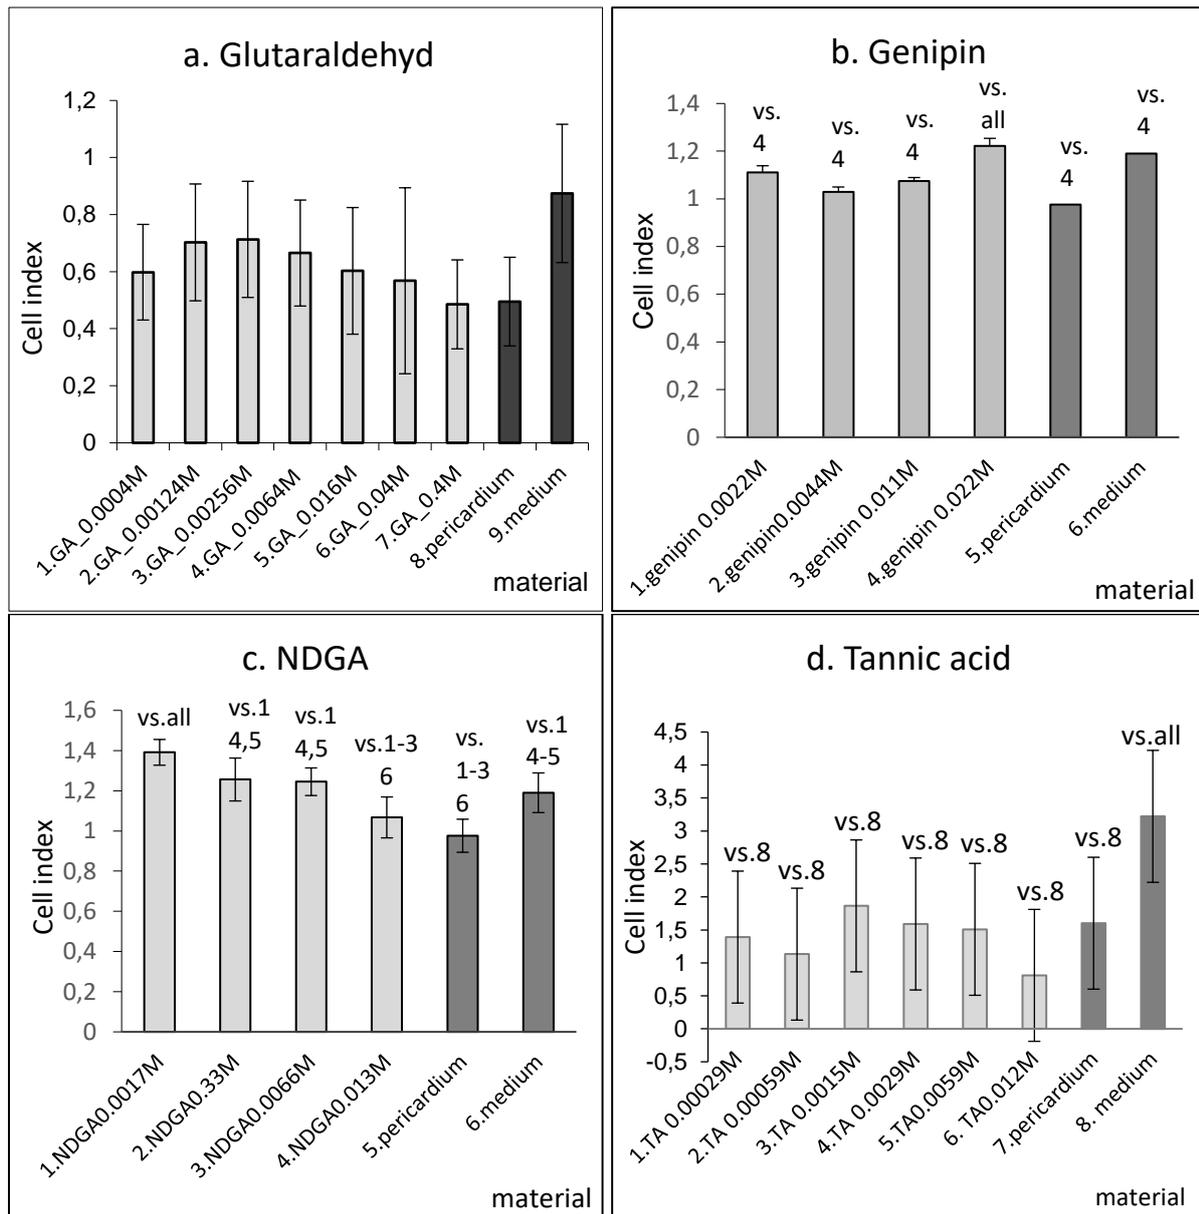

**Fig. 6.** Cell index of VIC cells on day 5 after cultivation in “elution medium” obtained by a 3-day elution of native human pericardium (pericardium) and pericardium cross-linked with (a) glutaraldehyde at concentrations of 0.0004, 0.001, 0.00256, 0.0064, 0.016, 0.04, and 0.4 M, with (b) genipin 0.0022, 0.0044, 0.011 and 0.022 M, and NDGA 0.0017, 0.0033, 0.0066, and 0.013 M, and with (c) tannic acid 0.00029, 0.00059, 0.0015, 0.0029, 0.0059, and 0.012 M. The data are presented as mean  $\pm$  S.D.; p value  $\leq 0.05$  is considered significant in comparison with the sample of the same number as depicted above the bars. Evaluated from 3-7 samples of each group, statistical analysis ANOVA, Student-Newman-Keuls method. The elution medium was

obtained after incubation of pericardium samples is DMEM supplemented with gentamicin for 3 days, into which 10% of FBS was added before cell seeding.